

The development of Aloe vera-based edible film with the addition of sago starch and glycerol for food packaging

by Ignasius Radix Ap Jati

Submission date: 09-Jul-2023 08:50PM (UTC+0700)

Submission ID: 2128442442

File name: The_development_of_aloe_vera__Radix.pdf (985.35K)

Word count: 5575

Character count: 28583

The development of *Aloe vera*-based edible film with the addition of sago starch and glycerol for food packaging

M S S Affandi, A R Utomo, E Setijawaty, L M Y D Darmoatmodjo and I R A P Jati*

Department of Food Technology, Widya Mandala Surabaya Catholic University, Jl. Dinoyo 42-44, Surabaya, Indonesia 60265

*Email: radix@ukwms.ac.id

Abstract. The edible film is a thin sheet material made of carbohydrates, protein or fat compounds. Research on the development of edible film is promising due to the increased plastic waste, which could disturb the environmental balance. The biodegradable nature of edible film provides an environmental-friendly material for packaging. Nevertheless, creating an edible film with similar properties to plastic will require extensive research. This research aims to develop *Aloe vera*-based edible film with the addition of sago starch as a texture enhancer and glycerol as a plasticizer and investigate the effect of different concentrations of sago starch on the physicochemical properties of edible film. In this research, six different concentration of sago starch was applied, which are 2.5%; 3%; 3.5%; 4%; 4.5%; and 5% (w/w). Each treatment was repeated four times. The result shows that the increase of sago starch concentration could increase the tensile strength and percent of elongation of edible film. On the contrary, the moisture content, water activity, and water vapor transmission rate (WVTR) were decreased. The range of tensile strength, percent of elongation, moisture content, water activity, and WVTR were 0.0254-0.4827 N/cm², 46.67%-61.79%, 13.39%-16.65%, 0.559-0.636, and 5.6460-10.0810 g/m²/hour, respectively.

1. Introduction

The Plastic is the most commonly used packaging material because it can protect products from contamination, minimize quality changes, have flexible characteristic, is lightweight, and possess affordable price [1]. However, the enormous utilization of plastic harms the environment because plastic is responsible for increasing non-biodegradable waste [2]. Based on the National Waste Management Information System (2021), the amount of plastic waste in Indonesia is the second largest after food waste, with approximately 27,717 tons per year. The accumulation of plastic waste will disturb the environmental balance, creating the problem of microplastic and water and soil pollution [3]. Efforts that can be taken to decrease the risk of environmental damage due to plastic waste are developing biodegradable materials as plastic alternatives, such as edible film.

Edible film is a thin layer material that can be utilized as food packaging and consumed along with the packaged product [4]. The materials used to make edible films are economically inexpensive, biodegradable, and simple to be produced. Edible films can be made from polymers, which are categorized into three groups, which are hydrocolloids (proteins, polysaccharides, and alginates), fats (fatty acids, acylglycerols, and waxes), and composites of both [5]. The polymer can be decomposed, so it is environmentally friendly. *Aloe vera* is one of the hydrocolloids that can be used to produce edible



film because it contains carbohydrate. Moreover, *A. vera* possesses high antioxidant and antimicrobial properties. Other components in *A. vera* are water, polysaccharides, amino acids, lipids, sterols, tannins, and enzymes [6]. Glucomannan is the polysaccharide in *A. vera* responsible for the ability to form a film. Glucomannan can bind a substantial amount of water, thus helping create a thin layer of film. Furthermore, glucomannan provides elasticity to the edible film [7]. Nevertheless, *A. vera* gel could not create a rigid characteristic of the film due to the limited number of substances responsible for constructing the structure. Therefore, *A. vera*-based films are commonly applied as an edible coating in various fruits and vegetables to prevent postharvest loss and prolong the shelf life of the commodities [8]. In order to increase the strength of *A. vera*-based edible film, compounds such as starch can be incorporated. Starch can act as a filler and matrix-forming substance in the edible film. Therefore, various starch such as cassava, corn, wheat and sago starch were widely reported as edible film ingredients [9]. Starch consists of two components, which are amylose and amylopectin. Amylopectin plays a role in the stability of edible films. Meanwhile, amylose plays a role in the compactness of edible films [10].

Sago starch that can be used to produce edible film has an amylose and amylopectin ratio of 27:73. Due to the high level of amylopectin, the edible film produced has a high permeability due to the effect of branched amylopectin structure [11]. In addition to amylopectin, sago starch has high amylose content (> 25%). Thus, it can produce a robust edible film because amylose can form hydrogen bonds among glucose molecules. When heated, it will form a three-dimensional network that can trap water. Due to starch retrogradation, high amylose content in sago starch incorporated into *A. vera*-based edible film will form a compact and stiff edible film [12]. An excessively firm edible film structure negatively affects the elasticity of the film. It can easily crumble when folded to create a packaging design. Therefore, adding plasticizer is crucial to improve the characteristics of edible films.

The presence of plasticizers will reduce the affinity of intra-molecular bonds among starch structures by forming hydrogen bonds between starch and plasticizers to improve the mechanical properties of edible films [13]. A plasticizer is an organic material with a low molecular weight that is applied to increase the flexibility of the polymer [14], such as glycerol and sorbitol. The capability of the hydrophilic group of glycerol to bind water is better than sorbitol. Therefore, the inclusion of glycerol in the edible film system could produce plastic-like film due to the ability to retain the moisture content in the edible film. Research on *A. vera* as an edible fruit and vegetable coating is widely reported. Meanwhile, the development of starch-based edible film using tapioca and corn starch are previously established. However, limited research is available on the inclusion of sago starch in the formulation of *A. vera*-based edible film enriched with glycerol. Therefore, this research aims to determine the effect of different concentrations of sago starch on the physicochemical properties of *A. vera*-based edible film using glycerol as a plasticizer.

2. Materials and Methods

2.1. Materials

A. vera was grown in Madiun District, East Java, and purchased Han Indo Jaya a national *A. vera* supplier in Sidoarjo District, East Java Province, Indonesia. The *A. vera* was harvested at six months, possesses a clean green skin color, is approximately 45±4.5 cm long, weighs around 350±35 g for each rind, and has the absence of injury on the surface of the rind. Meanwhile, the sago starch was purchased from the local market in Surabaya, and glycerol was obtained from Sigma Aldrich (Singapore).

2.2. Edible film preparation

Materials used in the formulation of *A. vera*-based edible film were *A. vera* gel, sago starch and glycerol. The formulation of ingredients is presented in Table 1. First, the *A. vera* rind was washed to remove the impurities. Then, trimmed, and the thick outer skin was peeled. Next, the gel fraction was washed with warm water to remove the yellow sap. The gel was then crushed using a blender and filtered through 80 mesh sieves to separate the gel from the solid fraction. The gel was then heated in an iron cast pot using

a stove at 80 °C for 5 min. After heating, the *A. vera* gel was allowed to cool to room temperature. Next, the *A. vera* gel, sago starch, and glycerol were placed in a beaker according to the formulation and gently stirred until a homogenous mixture was achieved. The mixture was then heated on a stove at 75 °C, kept for 3 minutes, and then cooled at room temperature until it reached 50 °C. After that, 25 g of the mixture was placed in a tray and spread uniformly in the size of 10 x 10 cm wide and 0.05 cm thick. The tray was placed in an air-conditioned room (18 °C) for 30 h. After completely drying, the film was removed from the tray, placed in polypropylene plastic, and stored until further used.

Table 1. Formulation of *A. vera*-based ² edible film

Materials	F1	F2	F3	F4	F5	F6
<i>A. vera</i> gel (g)	195	194	193	192	191	190
Sago starch (g)	5	6	7	8	9	10
Glycerol (g)	3.7	3.7	3.7	3.7	3.7	3.7
Total (g)	203.7	203.7	203.7	203.7	203.7	203.7

Note: The concentrations of sago starch (F1: 2.5%; F2: 3%; F3: 3.5%; F4: 4%; F5: 4.5%; and F6

2.3. Moisture content

The method used to analyze the moisture content of *A. vera*-based edible film was thermogravimetric [15]. In brief, the edible film was cut, and 0.5 g of the sample was put in a weighing bottle. The sample was then placed in the drying oven at 105 °C for 2 h. After that, the sample was cooled in a desiccator for 10 minutes before weighing. Repeat the step until the constant weight of the sample was achieved. Finally, the sample's moisture content is expressed as the moisture percentage within the sample.

⁴ 2.4. Water Activity

The water activity of *A. vera*-based edible film was measured using an Aw meter (HygroPalm AW1, Rotronic AG, Switzerland) [16]. Briefly, the edible film was cut into small pieces. 5 g of the edible film was placed in the specific chamber for the equipment. The machine was started and calibrated. Placed the chamber in the equipment, stored it, and let the equipment read the Aw value of the edible film.

⁹ 2.5. Water Vapor Transmission Rate (WVTR)

The WVTR determination was conducted according to previous method [17]. A total of 5 small glass chambers for each treatment were weighed to determine the initial weight of the glass. After that, 10 g of silica gel was put into the glass chamber. The mouth of the glass chamber was sealed using an edible film sample. The sealed glass was placed in the desiccator containing saturated sodium chloride solution. The edible film lid was removed every hour for 5 hours. Silica gel inside the glass chamber was removed, placed in a plastic container, and weighed. After that, the difference between the initial weight of silica gel and its final weight was determined. The data obtained were then analyzed using linear regression, and the slope was computed. The water vapor transmission rate was calculated using the following formula

$WVTR = \text{slope of the difference in weight of silica gel (g/h)/area of the mouth of the glass (m}^2\text{)}$

2.6. Tensile Strength and Percentage of Elongation

The experiment was conducted according to the ASTM D-882 method [18], the standard method to examine the tensile characteristic of plastic film. A texture analyzer equipment was used to measure the tensile strength. In brief, the sample was prepared by cutting the edible film into 145 x 10 mm size, and then each tip of the sample was clipped into the machine, and the machine will then drag the edible film in the opposite direction. The tensile strength of the edible film is calculated as the force needed to drag it until it breaks. Meanwhile, the elongation is the percentage of edible film length difference before and after being dragged by the texture analyzer.

2.7. Statistical Analysis

This research has 6 treatments, and each treatment was repeated four times. Data were analyzed using Analysis of Variance in $\alpha=5\%$ and Duncan Multiple Range Test (DMRT) to determine which treatments are significantly different. The statistical analysis was conducted using SPSS ver 23. The data were presented as means \pm standard deviation.

3. Result and Discussion

3.1. Moisture content

The results of moisture content determination of *A. vera*-based edible film with different concentrations of sago starch (F1-F6) were in the range of 13.39%-16.65%. Further analysis revealed a significant difference in the effect of sago starch concentration on the edible film's moisture content. The effect of sago starch concentration on the moisture content of *A. vera*-based edible films with the addition of glycerol can be seen in Figure 1.

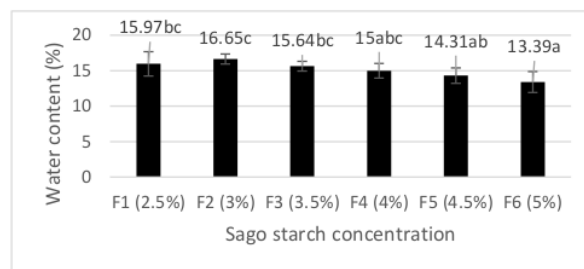


Figure 1. The moisture content of *A. vera*-based edible film

Based on Figure 1, the moisture content of the edible film tends to decrease along with the increase in the concentration of sago starch. The moisture content of edible film at 5% sago starch concentration was not significantly different from 4% and 4.5% sago starch concentrations (F4 and F5) but significantly different from 2.5%-3.5% sago starch concentrations (F1-F3). The difference is because, at 5% sago starch concentration (F6), the amount of water from the *A. vera* gel absorbed in the starch structure during gelatinization is higher due to the starch network activity to entrap water. The edible film was let dry at room temperature for 30 h. This process provides sufficient time for the edible film to dry and experience further retrogradation. In this process, a substantial amount of water is evaporated. Therefore, the moisture content in edible film in the F6 treatment is lower. At the concentration of sago starch 2.5%-3.5% (F1-F3), the amount of *A. vera* gel available in the formulation was higher compared to edible film with 5% sago starch concentration (F6), so the final moisture content at the concentration of 2.5%-3.5% (F1-F3) was higher and significantly different from the 5% sago starch concentration (F6). The phenomena could be due to *A. vera*, which contains glucomannan, a hydrocolloid, so it has better water binding ability [12]. It thus could absorb a substantial amount of water. Therefore, when the edible film was air dried at room temperature, the moisture content was retained in the film, thus resulting in higher moisture content.

The variation of starch concentration influencing the number of starch-glucomannan bonds formed leads to significant differences in the moisture content of the edible film, thus affecting their characteristic. For example, the edible film with a sago starch concentration of 2.5% (F1) has better characteristics than the 5% sago starch concentration (F6). Glucomannan contained in edible films has a vital role in binding and trapping water, thus could inhibit the transfer of water vapor from the environment to the product and vice versa. Edible film with a higher proportion of *A. vera* gel or a lower concentration of starch experienced a low rate of water evaporation. Therefore, the moisture content of the edible film is higher [19]. The results of this experiment are also supported by previous work by

Pinzon et al. [20]. They investigated the effect of starch incorporations on the characteristics of *A. vera*-based edible films. Increasing starch concentration in the edible film formulation will reduce the product's moisture content. The higher starch concentration increases the polymer available and gel viscosity during heating. The increasing number of polymers leads to the high absorption of water. The water available will then evaporate during the drying of edible film, resulting in a decrease in the moisture content. Based on the JIS standard [21], the maximum moisture content of the edible film is 13%. The *A. vera*-based edible film produced in this experiment had a moisture content ranging from 13.39%-16.65%. Therefore, the moisture content of *A. vera*-based edible film with different concentrations of sago starch produced is still higher than the existing standard.

3.2. Water Activity

A. vera-based edible film's water activity (A_w) results ranged from 0.559-0.636. The results were analyzed using ANOVA ($\alpha=5\%$), which shows a significant difference in the effect of the concentration of sago starch on the water activity of the edible film. The analysis was then continued with the DMRT test ($\alpha=5\%$), presented in Figure 2. The result shows that the lowest water activity value of the edible film was at 5% sago starch concentration (F6). The water activity tends to decrease when the starch concentration increases due to an increase in the amount of water bound to starch during gelatinization. During starch gelatinization, hydrogen bonds are broken so that more water will be absorbed by the starch granules, which is indicated by an increase in the viscosity of the gel mixture. Sago starch has approximately 35-38% amylose content [22]. Therefore, edible films with higher concentrations of sago starch will produce a physically dried film due to the retrogradation of gelatinized starch. At a lower concentration of sago starch, the amount of water bound to the starch is less than that of a more significant starch concentration so that at a similar drying time, it will produce high moisture content edible film due to the free water available.

Moreover, hydrocolloid added to the edible film formulation would reduce the product's water activity [23]. A study on the effect of sago starch concentration on the characteristic of products suggested that the increase of starch concentration leads to a decrease in the water activity of the products [24]. The lower water activity value in edible films indicates that there is limited free water available in edible films. Therefore, the lower A_w value could prolong the shelf life of the edible film. On the other hand, the higher water activity value increases the susceptibility of edible films to microorganism growth due to free water. Based on the results, *A. vera*-based edible film with various concentrations of sago starch has a water activity value higher than 0.6 as a critical A_w value for moulds, so proper cautions must be applied in the storage of the edible film.

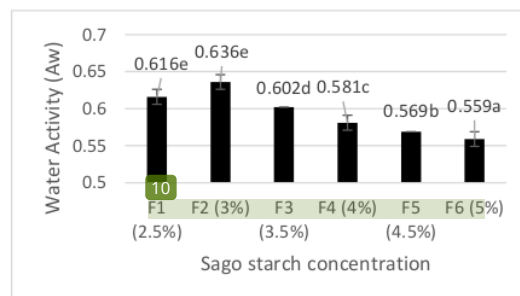


Figure 2. Water activity of *A. vera*-based edible film

3.3. Water Vapor Transmission Rate (WVTR)

The water vapor transmission rate (WVTR) was examined based on the changes in the weight of silica gel placed in a shot glass protected by *A. vera*-based edible film [25]. The WVTR aims to determine the permeability of edible films to water vapor in order to investigate its potential to be used as food

packaging. It is crucial to measure the WVTR because the water transmission rate of edible films can affect the shelf life of packaged products.

The results of the WVTR test of *A. vera*-based edible film with various concentrations of sago starch (F1-F6) and glycerol ranged from 5.6460-10.0810 g/m²/hour. The results of this WVTR test were analyzed using ANOVA ($\alpha=5\%$), which shows a significant difference in the effect of the concentration of sago starch on the WVTR of edible film. The analysis was then continued with the DMRT test ($\alpha=5\%$). The result of WVTR of *A. vera*-based edible films can be seen in Figure 3. The highest WVTR was achieved by the 2.5% and 3% of sago starch concentrations (F1-F2), and the lowest transmission rate was obtained by 4.5% and 5% of sago starch concentrations (F5-F6). The results show that the increase of sago starch concentration leads to the decrease of WVTR.

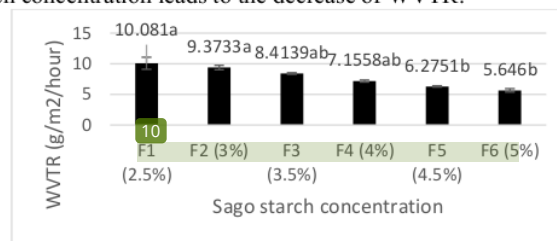


Figure 3. Water Vapor Transmission Rate (WVTR) of *A. vera*-based edible film

The amount of amylose and amylopectin influences the WVTR in the edible film. Based on the formulation, the increase in the concentration of sago starch was accompanied by a decrease in the *A. vera* gel so that the solids content in the mixture of 5% sago starch concentration treatment (F6) was the highest. The amylose content creates a network using hydrogen bonds to form a rigid structure. The presence of amylopectin that binds to glucomannan of *A. vera* plays an essential role in reducing the WVTR by forming a cross-linking network to minimize the exposure of amylopectin hydrophilic groups [26].

Meanwhile, Siskawardani et al. [27] examined the characteristics of edible films made of gembili tuber starch and *A. vera*. Zheng et al. [28] investigated the characteristics of edible films from starch and chitosan. Both studies showed that low concentrations of sago starch increase the WVTR, while the WVTR decreased with the increase of starch concentration. The presence of hydrogen bonds and cross-linking network at high concentrations of sago starch produces a rigid structure-edible film, causing a decrease in permeability. WVTR of edible films F1-F4 is higher than the JIS standard, while for F5 and F6, the WVTR is lower than the Japanese Industrial Standard (7 g/m²/hour) [21].

3.4. Tensile Strength and Percentage of Elongation

The results of the tensile strength ranged from 0.0254-0.4827 N/cm². Based on the analysis of variance ($\alpha=5\%$), a significant difference was observed and the analysis continued with DMRT. The result is presented in Figure 4. The highest tensile strength of the edible film was at 5% of sago starch concentration treatment (F6), and the lowest tensile strength was at 2.5% and 3% sago starch concentrations. The higher concentration of sago starch increased the tensile strength.

The tensile strength of edible films is influenced by two factors: the amount of amylose presents in the starch and the amount of glucomannan that interacts to form a cross-linking network with amylopectin. The higher starch concentration in edible film formulation provides more amylose so that the number of hydrogen bonds increases and can improve the tensile strength of edible films due to the strong hydrogen bonds formed [29]. The cross-links formed between amylopectin and acetyl groups in glucomannan also increase the edible film's tensile strength due to its solid and flexible properties.

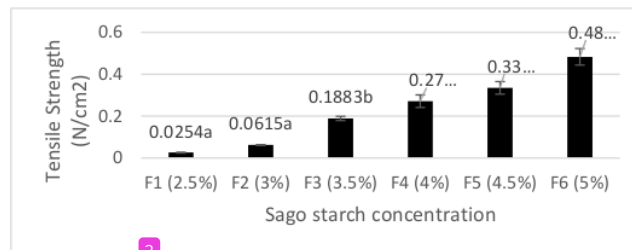


Figure 4. Tensile strength of *A. vera* based edible film

The results follow the previous work by Purnavita et al. [30] on the bioplastic characteristics of starch and glucomannan, as well as work by Zheng et al. [28] on the characteristics of edible films from starch and chitin. Both studies showed that a low starch concentration had a lower tensile strength and would improve with the increase of sago starch concentration. Based on the Japanese Industrial Standard, the standard value of the tensile strength of edible films is at least 30 N/cm² (0.3 Mpa). Therefore, the tensile strength in *A. vera*-based edible films was still below the JIS standard.

Meanwhile, the principle of elongation measurement is to determine the optimum length of the edible film to a certain point before it breaks. The elongation test is essential because of the need to produce flexible edible film packaging. The results show that the percent elongation ranged from 46.67-61.79% (Figure 5). The percent elongation of the edible film at a concentration of 3.5% to 5% (F3-F6) was not significantly different. The higher concentration of sago starch tends to increase the percentage of edible film elongation [29]. The elongation percentage of an edible film with 2.5% sago starch concentration was not significantly different from the 3% of the edible film with the lowest elongation percentage. Purnavita et al. [30] suggested that the higher content of amylose accompanied by the presence of glycerol in the edible film will produce a more flexible and robust film. In addition, cross-linking between glucomannan and amylopectin also plays a role in shaping the flexibility of the film. The number of polysaccharides that form the edible film determines its stretchability. The higher the polysaccharides present, the higher the film's resistance to fracture. Meanwhile, glucomannan and amylopectin will form a cross-linking network, and the presence of bonds between the hydroxyl groups on amylose and glycerol will improve the flexibility of the edible film. Based on the Japanese Industrial Standard, the standard value of the percent elongation of the edible film is less than 10% indicating an unfavorable elongation characteristic. Therefore, the percent elongation higher than 50% can be considered a suitable material. Compared to the JIS, *A. vera*-based edible films produced at 2.5%-5% sago starch concentration could be categorized as excellent material.

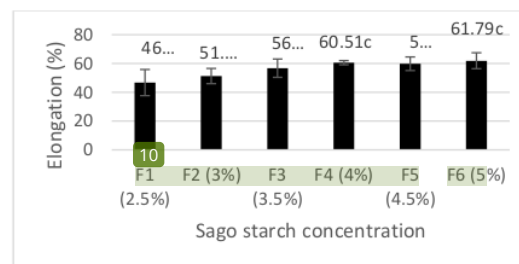


Figure 5. Percentage of Elongation of *A. vera* based edible film

4. Conclusions

Different concentrations of sago starch in the production of *A. vera*-based edible films with the addition of glycerol had a significant effect on moisture content, water activity (A_w), water vapor transmission rate (WVTR), tensile strength (tensile strength), and percentage of elongation. For example, sago starch

with concentrations of 2.5% to 5% tends to reduce the water content, water activity, and WVTR of *A. vera*-based edible film. On the other hand, the tensile strength and percentage of elongation were increased. Based on the result, *A. vera* gel could be used to produce the edible film by adding other hydrocolloids to improve its characteristics.

Acknowledgement

The authors are grateful to the Directorate of Research and Community Services, Deputy of Research Empowerment and Development, The Ministry of Education, Culture, Research and Technology, Republic of Indonesia for the funding of this research through research grant number 260K/WM01.5/N/2022

References

- [1] White A and Lockyer S 2020 Removing plastic packaging from fresh produce – what’s the impact? *Nutr Bull* **45** 35–50
- [2] Ncube L K, Ude A U, Ogunmuyiwa E N, Zulkifli R and Beas I N 2021 An Overview of Plastic Waste Generation and Management in Food Packaging Industries *Recycling* **6** 12
- [3] Leslie H A, van Velzen M J M, Brandsma S H, Vethaak A D, Garcia-Vallejo J J and Lamoree M H 2022 Discovery and quantification of plastic particle pollution in human blood *Environment International* **163** 107199
- [4] Chhikara S and Kumar D 2022 Edible Coating and Edible Film as Food Packaging Material: A Review *J Package Technol Res* **6** 1–10
- [5] Kumar L, Ramakanth D, Akhila K and Gaikwad K K 2022 Edible films and coatings for food packaging applications: a review *Environ Chem Lett* **20** 875–900
- [6] Maan A A, Reiad Ahmed Z F, Iqbal Khan M K, Riaz A and Nazir A 2021 Aloe vera gel, an excellent base material for edible films and coatings *Trends in Food Science & Technology* **116** 329–41
- [7] Akintayo O A, Obadu J M, Karim O R, Balogun M A, Kolawole F L and Oyeyinka S A 2019 Effect of replacement of cassava starch with sweet potato starch on the functional, pasting and sensory properties of tapioca grits *LWT* **111** 513–9
- [8] Athmaselvi K A, Sumitha P and Revathy B 2013 Development of Aloe vera based edible coating for tomato *International Agrophysics* **27** 369–75
- [9] Sahraee S, Milani J M, Regenstein J M and Kafil H S 2019 Protection of foods against oxidative deterioration using edible films and coatings: A review *Food Bioscience* **32** 100451
- [10] Fitriani Z A, Dieny F F, Margawati A and Jauharany F F 2021 Resistant starch, amylose, and amylopectin content in breadfruit cookies as an alternative snack for individuals with diabetes mellitus *Food Res.* **5** 394–400
- [11] Ma X, Chang P R and Yu J 2008 Properties of biodegradable thermoplastic pea starch/carboxymethyl cellulose and pea starch/microcrystalline cellulose composites *Carbohydrate Polymers* **72** 369–75
- [12] Hajebi Seyed R, Rastegar S and Faramarzi S 2021 Impact of edible coating derived from a combination of Aloe vera gel, chitosan and calcium chloride on maintain the quality of mango fruit at ambient temperature *Food Measure* **15** 2932–42
- [13] Liang T and Wang L 2018 Preparation and characterization of a novel edible film based on *Artemisia sphaerocephala* Krasch. gum: Effects of type and concentration of plasticizers *Food Hydrocolloids* **77** 502–8
- [14] Fongin S, Kawai K, Harnkarnsujarit N and Hagura Y 2017 Effects of water and maltodextrin on the glass transition temperature of freeze-dried mango pulp and an empirical model to predict plasticizing effect of water on dried fruits *Journal of Food Engineering* **210** 91–7
- [15] Jati I R A P, Darmaatmodjo L M Y D, Suseno T I P, Ristiarini S and Wibowo C 2022 Effect of Processing on Bioactive Compounds, Antioxidant Activity, Physicochemical, and Sensory

- Properties of Orange Sweet Potato, Red Rice, and Their Application for Flake Products *Plants* **11** 440
- [16] Vesterlund S, Salminen K and Salminen S 2012 Water activity in dry foods containing live probiotic bacteria should be carefully considered: A case study with *Lactobacillus rhamnosus* GG in flaxseed *International Journal of Food Microbiology* **157** 319–21
- [17] Putri Rr D A, Setiawan A and Anggraini P D 2017 Effect of carboxymethyl cellulose (CMC) as biopolymers to the edible film sorghum starch hydrophobicity characteristics ENGINEERING INTERNATIONAL CONFERENCE (EIC) 2016: Proceedings of the 5th International Conference on Education, Concept, and Application of Green Technology (Semarang, Indonesia) p 020044
- [18] Bousi C, Sismanidou O X, Marinopoulou A and Raphaelides S 2022 Effect of sugar addition on the elongational and shearing deformation behavior of sesame paste systems *LWT* **153** 112479
- [19] Nourozi F and Sayyari M 2020 Enrichment of Aloe vera gel with basil seed mucilage preserve bioactive compounds and postharvest quality of apricot fruits *Scientia Horticulturae* **262** 109041
- [20] Pinzon M I, Garcia O R and Villa C C 2018 The influence of *Aloe vera* gel incorporation on the physicochemical and mechanical properties of banana starch-chitosan edible films: Influence of *Aloe vera* gel incorporation on banana starch-chitosan edible films *J. Sci. Food Agric* **98** 4042–9
- [21] Santoso B, Sinaga T L D, Priyanto G, and Hermanto 2022 Effect of natural active compound addition on mechanical and functional properties of canna starch based edible film *Food Sci. Technol* **42** e51020
- [22] Du C, Jiang F, Jiang W, Ge W and Du S 2020 Physicochemical and structural properties of sago starch *International Journal of Biological Macromolecules* **164** 1785–93
- [23] Halimatul M J, Sapuan S M, Jawaid M, Ishak M R and Ilyas R A 2019 Effect of sago starch and plasticizer content on the properties of thermoplastic films: mechanical testing and cyclic soaking-drying *Polimery* **64** 422–31
- [24] Zhu F 2019 Recent advances in modifications and applications of sago starch *Food Hydrocolloids* **96** 412–23
- [25] Santoso B, Hazirah R, Priyanto G, Hermanto dan Sugito dan 2019 Utilization of *Uncaria gambir* Roxb filtrate in the formation of bioactive edible films based on corn starch *Food Sci. Technol* **39** 837–42
- [26] Saberian M, Seyedjafari E, Zargar S J, Mahdavi F S and Sanaei-rad P 2021 Fabrication and characterization of *alginate/chitosan* hydrogel combined with *honey* and *ALOE VERA* for wound dressing applications *J Appl Polym Sci* **138** 51398
- [27] Siskawardani D D, Warkoyo W and Siwi A A P 2020 The Effect of Aloe vera and Glycerol Addition on Edible Film of Lesser Yam Starch (*Dioscorea esculenta* L. Burkill) *Food Technol. Halal Sci.* **3** 26
- [28] Zheng K, Xiao S, Li W, Wang W, Chen H, Yang F and Qin C 2019 Chitosan-acorn starch-eugenol edible film: Physico-chemical, barrier, antimicrobial, antioxidant and structural properties *International Journal of Biological Macromolecules* **135** 344–52
- [29] Sandhu K S, Sharma L, Kaur M and Kaur R 2020 Physical, structural and thermal properties of composite edible films prepared from pearl millet starch and carrageenan gum: Process optimization using response surface methodology *International Journal of Biological Macromolecules* **143** 704–13
- [30] Purnavita S, Subandriyo D Y and Anggraeni A 2020 Penambahan Gliserol terhadap Karakteristik Bioplastik dari Komposit Pati Aren dan Glukomanan *METANA* **16** 19–25

The development of Aloe vera-based edible film with the addition of sago starch and glycerol for food packaging

ORIGINALITY REPORT

9%

SIMILARITY INDEX

5%

INTERNET SOURCES

9%

PUBLICATIONS

0%

STUDENT PAPERS

PRIMARY SOURCES

- 1** ouci.dntb.gov.ua 2%
Internet Source
- 2** Rian Adhi Santoso, Yoni Atma. "Physical Properties of Edible Films from Pangasius catfish Bone Gelatin-Breadfruits Strach with Different Formulations", Indonesian Food Science & Technology Journal, 2020 1%
Publication
- 3** Riska Surya Ningrum, Dewi Sondari, Putri Amanda, Bernadeta Ayu Widyaningrum, Dian Burhani, Fazhar Akbar, Yulianti Sampora. "PROPERTIES OF EDIBLE FILM FROM MODIFIED SAGO STARCH PRECIPITATED BY BUTANOL", Jurnal Sains Materi Indonesia, 2020 1%
Publication
- 4** Anupama Semwal, Kiran Ambatipudi, Naveen Kumar Navani. "Development and characterization of sodium caseinate based probiotic edible film with chia mucilage as a

protectant for the safe delivery of probiotics in functional bakery", Food Hydrocolloids for Health, 2022

Publication

5

myscholar.umk.edu.my

Internet Source

1 %

6

M. Javanmard, N.L. Chin, Y.A. Yusof, J. Endan. "Application of sago starch as a gelling agent in jam", CyTA - Journal of Food, 2012

Publication

1 %

7

"Polymers for Agri-Food Applications", Springer Science and Business Media LLC, 2019

Publication

1 %

8

Siti Hajar OTHMAN, Siti Amirah Mohammad EDWAL, Nazratul Putri RISYON, Roseliza Kadir BASHA, Rosnita A. TALIB. "Water sorption and water permeability properties of edible film made from potato peel waste", Food Science and Technology, 2017

Publication

1 %

9

Giyatmi Giyatmi, Tika Annisa Eka Poetri, Hari Eko Irianto, Dina Fransiska, Agusman Agusman. "Effect of Alginate and Polyethylene Glycol Addition on Physical and Mechanical Characteristics of k-Carrageenan-based Edible Film", Squalen Bulletin of Marine and Fisheries Postharvest and Biotechnology, 2020

1 %

10

www.chesuccede.it

Internet Source

1 %

11

www.veterinaryworld.org

Internet Source

1 %

Exclude quotes On

Exclude matches < 1%

Exclude bibliography On